

Elaboration and Characterization of CuO Thin Films by Spray Pyrolysis Method for Gas Sensors Applications

Maha Hinna ^{1,*}, Bouchaib Hartiti ¹, Abdelkrim Batan ^{1,2}, François Reniers ³,
Claudine Buess-Herman ³, Tiriana Segato ⁴, Naoual Belouaggadia ¹, Salah Fadili ¹, Maryam Siadat ⁵
and Philippe Thévenin ⁶

¹ MEEM & DD Group, Hassan II University of Casablanca, FSTM 28800 Mohammedia, Morocco; bhartiti@gmail.com (B.H.); kbatan@gmail.com (A.B.); n.belouaggadia@gmail.com (N.B.); safadili@yahoo.fr (S.F.)

² Materials Science Team, Department of Chemistry, Faculty of Sciences and Techniques Errachidia, University Moulay Ismail, 50050 Errachidia, Morocco

³ Analytical and Interfacial Chemistry, Department of Chemistry, Faculty of Sciences, Free University of Brussels, 1050 Brussels, Belgium; Francois.Reniers@ulb.ac.be (F.R.); Claudine.Buess-Herman@ulb.ac.be (C. B.-H.)

⁴ 4MAT Laboratory, Polytechnic School of Brussels, Free University of Brussels, 1050 Brussels, Belgium; Tiriana.Segato@ulb.ac.be

⁵ LCOMS Laboratory, Department of physics, University of Lorraine, 57000 Metz, France; maryam.siadat@univ-lorraine.fr

⁶ LMOPS Laboratory, Department of physics, University of Lorraine, 57000 Metz, France; philippe.thevenin@univ-lorraine.fr

* Correspondence: maha.hinna@gmail.com; Tel.: +21-266-005-0071

† Presented at the 8th GOSPEL Workshop. Gas Sensors Based on Semiconducting Metal Oxides: Basic Understanding & Application Fields, Ferrara, Italy, 20–21 June 2019.

Published: 28 June 2019

Abstract: Metal oxide semiconductor gas sensors are used in a various applications in environmental, industrial and medical field, for instance. They are relatively inexpensive compared to other sensing technologies, robust, lightweight, long lasting and benefit from high material sensitivity and quick response times. Copper oxide (CuO) thin film has been promisingly proposed for chemical sensing applications. Particularly, it has been recommended as a sensitive layer for monitoring harmful and combustible gases. It is an attractive material because of nontoxic, inexpensive, abundance advantages, and its fabrication is easy. In this work, we have synthesized CuO thin films by Spray pyrolysis method. The effect of the temperature deposition is investigated: to say 350 °C, 400 °C, and 450 °C while the deposition duration was kipped to 15 min. The samples were analyzed by X-ray diffraction, Raman spectroscopy, XPS analysis, UV-visible transmission and four points probe method.

Keywords: CuO; spray pyrolysis; deposition temperature effect; gas sensors

1. Experimental

The solution for CuO was prepared by dissolving copper chloride (II) (CuCl₂) in distilled water; the solution has been stirred at 60 °C during 30 min. The ordinary glass substrates were cleaned with diluting nitric acid, acetone, ethanol, and distilled water. Spray pyrolysis was employed to deposit the CuO solution on the ordinary glass substrates, during 15 min at different temperatures including 350 °C, 400 °C, and 450 °C. The prepared films were analyzed using an X-ray diffractometer, spectroscopy Raman, XPS analysis, UV-visible spectrometer and 4-point probe method to the calculated sheet resistance and resistivity.

2. Characterization

The crystalline phase of the films was characterized by X-Ray diffraction DRX. In the Figure 1 we have the X-Ray diffraction spectrum of copper oxide (CuO) at various substrate temperatures deposition. In the other side, we have Raman spectrum of CuO whose mentions the Ag(1), Bg(1), and Bg(2) modes located at 290, 338, and 626 (Figure 2). The Raman spectroscopy confirms the CuO phase formation proved by DRX data.

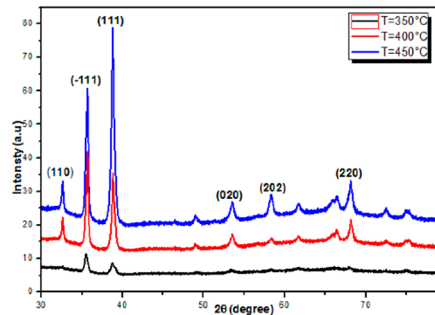


Figure 1. X-ray diffraction patterns of CuO thin films deposited at various substrate temperatures.

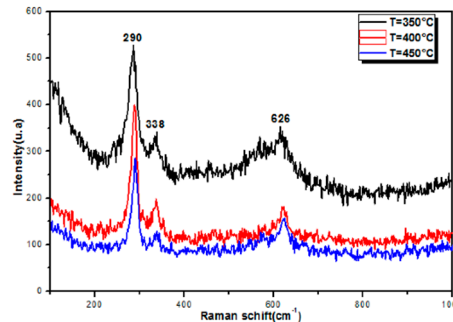


Figure 2. Raman spectra of CuO thin films deposited at 350 °C, 400 °C and 450 °C.

3. Conclusions

The X-ray diffraction peaks at (110), (-111), (-202), (020), (-113) and (220) plans indicate the formation of CuO thin films. Raman scattering measurements confirm the existence of CuO by peaks at 290, 338 and 626 cm^{-1} . XPS analysis also shows peaks indicating the presence of copper and oxygen. Band gap has been calculated according to the transmission measurements. We observe that the gap decreases while the substrate deposition temperature increases, and in contrary, the sheet resistance of these films increases when the substrate deposition temperature increases. These results make CuO thin films elaborated using spray pyrolysis set up, favourable for gas sensors applications.

Acknowledgments: This research is performed with the support of the Franco-Moroccan PHC Toubkal program.

Conflicts of Interest: The authors declare no conflict of interest.



© 2019 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).